


PARAPRO GREEN ROOF SYSTEM

CONCRETE (non-nailable)

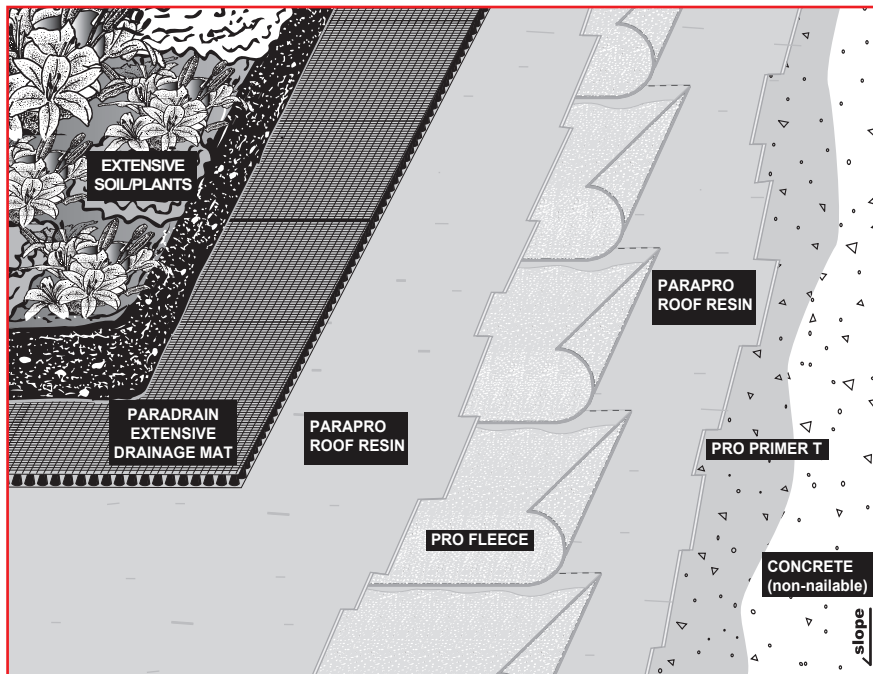

n.t.s.

| | |
|----------------------------------|--|
| SLOPE MATERIALS | 0" to 1" per foot min.* per 100 sq ft |
| PRO PRIMER T | 3.7 kg |
| PARAPRO ROOF RESIN | 19 kg |
| PRO FLEECE | |
| PARAPRO ROOF RESIN | 12 kg |
| PARADRAIN EXTENSIVE DRAINAGE MAT | 25 lb |
| SOIL/PLANTS | |

Requirements and recommendations detailed in the Siplast catalog and Siplast long form specifications shall apply in addition to the following recommendations and specifications.

Application

1. Where required, apply an even coat of catalyzed Pro Primer T over the prepared concrete surface using an approved roller at the rate of 3.7 kilograms per square.
2. Apply an even, generous base coat of catalyzed Parapro Roof Resin over the primed concrete surface using an approved roller at a rate of 19 kilograms per square.
3. While the previously applied catalyzed Parapro Roof Resin is still wet, install Pro Fleece reinforcement, embedding the fleece into the resin using a roller. Ensure that no air is trapped beneath the fleece. Lap the fleece a minimum 2 inches side and end, and apply an additional coat of catalyzed Parapro Roof Resin between layers of overlapping fleece.
4. Immediately following embedment of the Pro Fleece reinforcement, apply an even, generous top coat of catalyzed Parapro Roof Resin at a rate of 12 kilograms per square, ensuring full saturation of the fleece.
5. Lay one layer of Paradrain Extensive Drainage Mat dry over the finished Parapro surface.
6. Install soil and plants as specified.

Ref #: Concrete - Ppro - Drainage Mat - Extensive Plants
Rev: 1.8.19